arXiv:cond-mat/9804219v3 [cond-mat.str-el] 19 Mar 1999

Magnetism of Stripe-Ordered $La_{5/3}Sr_{1/3}NiO_4$

Y. Yoshinari,[1] P. C. Hammel[1] and S-W. Cheong[2]
[1] *Los Alamos National Laboratory, Los Alamos, New Mexico 87545*
[2] *Lucent Technologies, Bell Laboratories, Murray Hill, New Jersey 07974*

(Version date: February 4, 1999)

^{139}La nuclear magnetic resonance studies reveal markedly different magnetic properties of the two sites created by the charged domain wall formation in $La_{5/3}Sr_{1/3}NiO_4$. NMR is slow compared to neutron scattering; we observe a 30 K suppression in magnetic ordering temperature indicating glassy behavior. Applied magnetic field reorients the in-plane ordered moments with respect to the lattice, but the relative orientation of the spins amongst themselves is stiff and broadly distributed.

PACS Numbers: 76.60.-k, 74.72.Bk, 75.30.Ds, 75.40.Gb

Since the discovery of high temperature superconductivity in the cuprates, the behavior of holes added to a strongly correlated two dimensional (2D) antiferromagnet has been a subject of intense interest. One important aspect of this system is its tendency toward inhomogeneous charge distribution [1]. In particular, segregation of doped holes into periodic arrays of charged stripes separating hole-free domains has been predicted [2]. Stripe ordering has been observed in doped La_2NiO_4 [3–6] which remains semiconducting up to very high Sr content [7]. The recent observation of similar elastic superlattice peaks in the isostructural [8,9] high-T_c superconductor $La_{1.48}Nd_{0.4}Sr_{0.12}CuO_4$ [10] indicates the existence of similar charge ordered structures, and suggests these structures may be relevant to cuprate superconductivity [11–14]. Similarities between these elastic superlattice peaks and the incommensurate peaks observed in inelastic neutron studies of $La_{2-x}Sr_xCuO_4$ [15] have been noted [16]. Hence, these incommensurate peaks are being reconsidered as possible evidence for the presence of dynamic charged stripes in the cuprate [16].

There is clear evidence for stripe formation in doped 2D AF systems [3–6], but detailed microscopic studies of their low energy dynamic and static magnetic properties are lacking. A detailed elastic neutron diffraction study of the title compound [6] has demonstrated charge ordering at $T_{\rm co} = 240\,{\rm K}$ [6,17,18] into domain walls or "stripes." The stripes run along two equivalent diagonal directions $\vec{e} = (1, 1)$ or $(1, \bar{1})$ in the tetragonal unit cell with dimensions $a_t \times a_t$ in the basal plane where a_t is the is the lattice parameter corresponding to the Ni-Ni spacing. The stripe period perpendicular to the stripes is $3a_t/\sqrt{2}$. At $T_{\rm so}^{\rm NS} = 190\,{\rm K}$, spin superlattice peaks appear indicating ordering of the spins between the stripes. Three temperature regions were evident, the highest between $T_{\rm so}^{\rm NS}$ and $T_{\rm co}$ exhibited elastic charge order peaks with weaker intensity and significantly reduced correlation lengths compared to lower temperatures. The authors proposed the existence of a "stripe glass" in this temperature regime, but were unable to study the very important issue of orientational order due to the dominant affect of short stripes. Below $T_{\rm so}^{\rm NS}$ the charge stripe order was found to improve.

In this Letter we report a single crystal ^{139}La NMR study of the two magnetically distinct sites observed below $T_{\rm co}$, the first located in the domain walls, and the second in the hole-free domains. Although the two regions are spatially proximate and strongly interacting, their static and dynamic magnetic properties are quite different. The NMR provides specific evidence in support of the stripe-glass hypothesis and reveals pronounced and unusual spin disorder arising from stripe defects. A hallmark of glassy systems is sensitivity of the transition temperature to measurement time scale; we find the onset of spin ordering at $T_{\rm so}^{\rm NMR} = 160\,{\rm K}$ in the NMR measurement is 30 K lower than $T_{\rm so}^{\rm NS}$ as a consequence of its slower characteristic time scale (μsec compared to psec for the neutron measurement). At low temperature where charge order becomes very good, the static spin order exhibits a continuous distribution of moment magnitudes and in-plane orientations. The $H_0 \perp c$ lineshape demonstrates that the ordered moments rotate in response to the applied field such that the most probable spin orientation is perpendicular to the applied field. However the broad continuous distribution reveals "stiffness" of the spin texture: defects in the charge order (stripe ends or bifurcations) frustrate the spin order causing the orientation of the in-plane ordered moments to rotate relative to each other. Finally, the NMR measurements rule out motion of domain walls below $T_{\rm co}$.

A local probe of electronic properties, nuclear magnetic resonance (NMR) is well suited to determining the microscopic properties of inhomogeneous structures. ^{139}La NMR is employed because ^{61}Ni NMR is not readily performed. In $La_{2-x}Sr_xNiO_4$ a given ^{139}La nucleus ($I = 7/2$, gyromagnetic ratio $\gamma = 601.44\,{\rm Hz/Oe}$) directly probes the magnetic properties of only one Ni electronic spin moment. This is because the transferred hyperfine coupling of the ^{139}La nuclear spin to the single Ni site that shares the La-apical O-Ni bond is an order of magnitude larger than its coupling to any of its four other Ni neighbors. In the Ni^{2+} ($3d^8$) ionic state, the two unpaired spins occupy the in-plane $3d_{x^2\text{-}y^2}$ and the out-of-plane $3d_{3z^2\text{-}r^2}$ atomic orbitals. The latter spin is particularly

FIG. 2. (a) The T-dependence of I_B, the B-peak fraction of the total intensity with $H_0 \parallel c$ (●), and of the broad peak fraction for $H_0 \perp c$ (△). (b) The T-dependencies of the total ^{139}La shift below $T_{\rm so}^{\rm NMR}$ for the B-peak (○) and the Knight shifts K for $H_0 \| c$ (plotted against the right-hand axis): A-peak (□) and B-peak (●). The open circles indicate the total shift below $T_{\rm so}^{\rm NMR}$. $H_{\rm int}$ is plotted against the left-hand axis. The solid line is a guide to the eye. (c) T-dependencies of the ^{139}La $T_1^{-1}$for $H_0 \parallel c$: A- (□) and B-peak (●); and for $H_0 \perp c$ (△); all measured at 48.5 MHz. T_1^{-1} for the A-peak with $H_0 \| c$ at 27 MHz (×) is also shown.

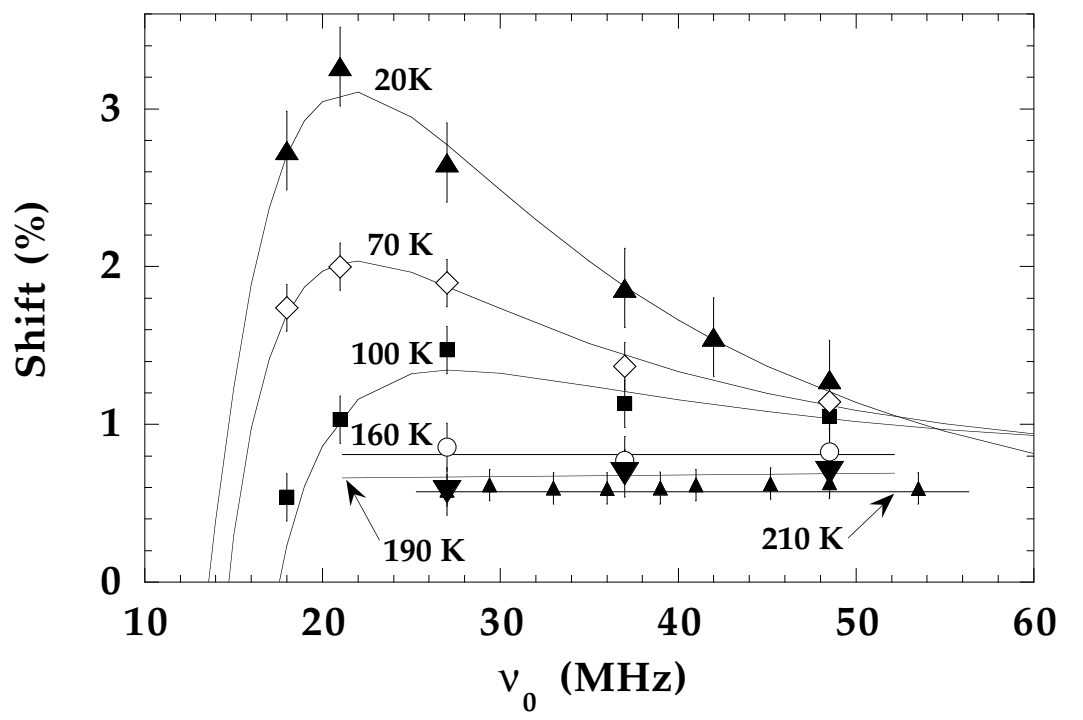

FIG. 3. The ν_0 dependence of the B-peak shift is shown for $H_0\|c$ for various T. The lines show fits to a model incorporating quadrupole interactions and an internal field lying in the planes ($\perp c$); see Eq. 1 and following text.

moments lie in the NiO$_2$ planes [5], their internal field adds to the applied field in quadrature $\left(H_{\text{eff}}^2 = H_0^2 + H_{\text{int}}^2\right)$. Thus, they do not produce the large shift one would expect based on the value of $A_{ab} = 20\,\text{kOe}/\mu_B$. The $\nu_0(=\gamma H_0)$ dependence of the shift is shown at several temperatures for $H_0\|c$ in Fig. 3. Understanding the field dependence requires taking account of the quadrupole interaction which produces a large negative shift at low applied fields $\left(\propto -\nu_Q^2/\nu_0^2\right)$. Exact diagonalization of the Hamiltonian

$$\frac{\mathcal{H}}{h} = (1+K)\nu_0 I_z + \frac{\nu_Q}{2}\left[I_z^2 - \frac{I(I+1)}{3}\right] + \nu_{\text{int}} I_x \qquad (1)$$

(with $z \parallel c$, and assuming that the moment lies in the plane) provides excellent fits (solid lines) to the measured field-dependent shifts. The quadrupole frequency ν_Q was monitored and varies by less than 10%; this has negligible affect on the determination of ν_{int}. The T-dependence of the internal magnetic field ($H_{\text{int}} = \nu_{\text{int}}/\gamma$) deduced from these fits is shown in Fig. 2(b). We observe no internal field in the 30 K region between $T_{\text{so}}^{\text{NS}}$ where superlattice peaks are first observed and $T_{\text{so}}^{\text{NMR}}$ below which an internal field is observed. At 20 K $H_{\text{int}} \simeq 14\,\text{kOe}$ at the La site, implying a Ni spin polarization $\langle S\rangle\,\mu_B = H_{\text{int}}/A_{ab} \approx 0.7\mu_B$. The growth of H_{int} below $T_{\text{so}}^{\text{NMR}}$ is unusually slow; this indicates suppression of the ordered moment by strong magnetic fluctuations.

At higher temperatures, in the absence of an internal field, the Knight shift K is given by Eq. 1 with $\nu_{\text{int}} = 0$. Above $T_{\text{so}}^{\text{NMR}}$ the $H_0\|c$ shifts for the A- and B-sites are essentially independent of ν_0, demonstrating that they are both exclusively magnetic in origin. The T-dependence of K is shown in Fig. 2(b). K^A for the A-sites decreases below T_{co}, while K^B for the B-sites increases strongly reaching $\sim 0.8\%$ at $T_{\text{so}}^{\text{NMR}}$. This large increase in K^B cannot be attributed to a variation in the hyperfine coupling since a shift in A would have a much more dramatic effect on T_1^{-1} ($\propto A^2$) which is not observed; furthermore, the variation of the lattice parameter is smooth across T_{co} and elsewhere [27]. Therefore, the large magnetic shift of the B-sites indicates an anomalously large susceptibility in the magnetic domains between stripes. When the contribution of the static field to the shift is taken into account we find that K^B decreases significantly below $T_{\text{so}}^{\text{NMR}}$, indicating a hardening of the ordered spins to a field applied perpendicular to the orientation of the ordered moments.

Substantial disordering of the in-plane orientation of the static moments is evident from the broad $H_0 \perp c$ line [Fig. 1(b)]. The internal field due to the antiferromagnetically ordered moment can vary from parallel to anti-parallel orientation relative to the field applied in the plane, causing shifts comparable to the internal field. The half-width of the $H_0 \perp c$ line is consistent with the $\sim 12\,\text{kOe}$ ordered moment detected in $H_0 \parallel c$ measurements. An orientationally ordered moment would produce discrete lines with shifts determined by the orientation of the ordered moment relative to the applied field; on the other hand, a completely random distribution of in-plane orientations would generate a two-dimensional powder pattern spectrum with singularities at its extrema [distribution $P(\Delta\nu)$ of frequency shifts $\sim 1/\sqrt{(\gamma H_{\text{int}})^2 - (\Delta\nu)^2}$]. Neither is seen; instead, the broad spectrum peaked at very small shift indicates that the most probable in-plane spin orientation is perpendicular to the applied field. This is the usual response of an ordered antiferromagnet since this allows a slight canting of the moments in response to the field. However, the broad width demonstrates a broad distribution of orientations around the perpendicular orientation. Thus, an applied field easily rotates the moments in the plane with respect to the lattice (and, hence, the ordered stripe structure), but the broad distribution of orientations of the moments relative to one another is unchanged by applied field. This is not due to a fortuitous choice of field orientation: the twinning of the stripe orientation would produce two populations of ordered moments rotated 90° with respect to each other, but the spectrum shows no evidence of a second, rotated spin population. This in-plane "twisting" of the spin texture by stripe defects presumably occurs over length scales comparable to the spin coherence length observed with neutrons ($\sim 100\,\text{Å}$ [6]).

The temperature dependencies of T_1^{-1} for the two environments [shown in Fig. 2(c)] are very different; two transitions occur in the hole-free domains (B-line) with little effect on spin dynamics in the domain walls (A-line). At all temperatures signal recoveries demonstrate a single T_1 and no signal intensity is lost. Below T_{co}, T_1^{-1} at the A-sites is monotonic in temperature down to 100 K. In contrast, T_1^{-1} at the B-sites shows a distinct and unusual *negative-going* cusp at $T_{\text{so}}^{\text{NS}}$ that clearly signals the transition at which spin-superlattice peaks appear in the neutron measurements [6]. This demonstrates the suppression of spin ordering in NMR is not a consequence of sample variability since the transition at $T_{\text{so}}^{\text{NS}}$ is clearly observed in our NMR measurements. A typical magnetic ordering transition would generate a *positive* cusp or divergence in T_1^{-1} at the ordering temperature (see e.g., Ref. [28]). The increase of T_1^{-1} toward a strong peak at lower temperature ~ 160 K indicates a rapid slowing of collective spin fluctuations indicative of long-range, 3D magnetic order at this temperature. The appearance of the internal field at the same temperature would naturally be interpreted as a magnetic transition, were it not that the spin-superlattice peak in neutron scattering occurs at the higher temperature.

This contrast in apparent ordering temperatures suggests sensitivity to measurement time scale. Rotation of the ordered moment (which is slow compared to the inverse of the energy resolution of the neutron measurement) could motionally average, and thus, reduce the measured H_{int}. $T_{\mathrm{so}}^{\mathrm{NMR}}$ would then correspond to the temperature at which this motion becomes slow on the NMR time scale ($\sim$ microseconds corresponding to $< 0.1\mu$eV). Our results rule out motion of domain walls below T_{co} even on the NMR time scale, as we observe distinct relaxation rates for the two sites immediately below T_{co} [25,29]. A second possibility is that the magnetic order is sufficiently sensitive to the applied magnetic field that it is suppressed between 160 and 195K.

In summary, the onset of magnetic order in charge-stripe ordered $La_{5/3}Sr_{1/3}NiO_4$ is suppressed by 30 K when detected on the μsec time scale of NMR compared to psec for neutron diffraction; this provides strong and specific evidence in support of the glassy character of the stripe order. The interplay between spin and charge order is evident in the very broad NMR line found at low temperature where the stripes are relatively well ordered. This probably arises from the strong spin disordering affects of defects (stripe ends and bifurcations) in the charge stripe pattern. These defects induce a distribution of *relative* spin orientations. However, the collection of spins as a whole is easily reoriented with respect to the lattice by an applied magnetic field. Finally, below the charge ordering temperature, the ordered charge stripes themselves are static on the NMR time scale.

We gratefully acknowledge stimulating discussions with A. R. Bishop, D. E. MacLaughlin, A. J. Millis, Byoung Jin Suh and Z. G. Yu. One of us (PCH) appreciates the contributions of J. Zaanen to our understanding of these results. Work at Los Alamos was supported by the Department of Energy, Office of Basic Energy Sciences.

---

[1] *Proceedings of the Workshop on Phase Separation in Cuprate Superconductors*, edited by K. A. Müller and G. Benedek (World Scientific, Singapore, 1993).

[2] J. Zaanen and O. Gunnarsson, Phys. Rev. B **40**, 7391 (1989); D. Poilblanc and T. M. Rice, Phys. Rev. B **39**, 9749 (1989); H. J. Schulz, J. Phys. (Paris), **50**, 2833 (1989); V. J. Emery, S. A. Kivelson and H. Q. Lin, Phys. Rev. Lett. **64**, 475 (1990); H. E. Viertiö and T. M. Rice, J. Phys. Condens. Matter **6**, 7091 (1994); J. Zaanen and P. B. Littlewood, Phys. Rev. B **50**, 7222 (1994); and S. R. White and D. J. Scalapino, Phys. Rev. Lett. **80**, 1272 (1998).

[3] S. M. Hayden *et al.*, Phys. Rev. Lett. **68**, 1061 (1992).

[4] C. H. Chen, S-W. Cheong and A. S. Cooper, Phys. Rev. Lett. **71**, 2461 (1993).

[5] J. M. Tranquada *et al.*, Phys. Rev. Lett. **73**, 1003 (1994); J. M. Tranquada, D. J. Buttrey and V. Sachan, Phys. Rev. B **54**, 12318 (1996).

[6] S.-H. Lee and S-W. Cheong, Phys. Rev. Lett. **79**, 2514 (1997).

[7] S-W. Cheong *et al.*, Phys. Rev. B **49**, 7088 (1994).

[8] J. D. Jorgenson *et al.*, Phys. Rev. B **40**, 2187 (1989).

[9] G. Aeppli and D. J. Buttrey, Phys. Rev. Lett. **61**, 203 (1988); K. Nakajima *et al.*, Z. Phys. B **96**, 479 (1995).

[10] J. M. Tranquada *et al.*, Nature, **375**, 561 (1995);

[11] V. J. Emery and S. A. Kivelson, O. Zachar, Phys. Rev. B **56**, 6120 (1997).

[12] J. M. Tranquada *et al.*, Phys. Rev. Lett. **78**, 338 (1997).

[13] J. Zaanen, M. L. Horbach and W. van Saarloos, Phys. Rev. B **53**, 8671 (1996).

[14] A. H. Castro Neto and F. Guinea, Phys. Rev. Lett. **80**, 4040 (1998).

[15] S-W. Cheong *et al.*, Phys. Rev. Lett. **67**, 1791 (1991).

[16] J. M. Tranquada, Physica C **282**, 166 (1997).

[17] A. P. Ramirez *et al.*, Phys. Rev. Lett. **76**, 447 (1996).

[18] G. Blumberg, M. V. Klein and S-W. Cheong, Phys. Rev. Lett. **80**, 564 (1998).

[19] A. M. Clogston and V. Jaccarino, Phys. Rev. **121**, 1357 (1961)

[20] S. Wada, *et al.,* J. Phys. Soc. Jpn. **58**, 2658 (1989).

[21] Cu NQR measurements in La_2CuO_4 indicate the transferred hyperfine coupling to the four nearest Ni sites via the La(6s) orbital will be of the same order as the dipole field; H. Nishihara *et al.*, J. Phys. Soc. Jpn. **56**, 4559 (1987).

[22] C. P. Slichter, *Principles of Magnetic Resonance*, 3rd ed. (Springer-Verlag, New York, 1990); A. Abragam *The Principles of Nuclear Magnetism*, (Oxford University Press, London, 1961).

[23] ν_Q was found to be significantly distributed at all temperatures (at 300 K $\nu_Q \simeq 4.55$ MHz with width 1.7 MHz). Essentially no change in ν_Q was observed at T_{co}.

[24] A. Narath, Phys. Rev. **162**, 320 (1967); D. E. MacLaughlin *et al.*, Phys. Rev. B **4**, 60 (1971).

[25] We carefully explored the possibility of charge stripe motion [29]. The absence of frequency dependence in T_1^{-1} and the sharp difference in T_1^{-1} at the two sites demonstrates that the charge stripes are static on the time scale 10^{-3} s.

[26] Between 190 K and T_{co} intensity was estimated by fitting each peak with a single Gaussian; below 190 K a product of a Gaussian and Lorentzian was used. By varying τ a nearly pure A-peak spectrum was obtained which confirmed that this deconvolution method nicely reproduces the observed lineshape. The single exponential spin-echo decay over more than a decade verifies the single-component nature of each peak [29].

[27] S. H. Han *et al.*, Phys. Rev. B **52**, 1347 (1995).

[28] B. J. Suh *et al.*, Phys. Rev. Lett. **75**, 2212 (1995).

[29] Y. Yoshinari *et al.*, to be published.